

# Parity-Affected Superconductivity in Ultrasmall Metallic Grains

Jan von Delft<sup>a</sup>, Dmitrii S. Golubev<sup>b</sup>, Wolfgang Tichy<sup>a</sup>, Andrei D. Zaikin<sup>a,b</sup>

<sup>a</sup> *Institut für Theoretische Festkörperphysik, Universität Karlsruhe, 76128 Karlsruhe, Germany*

<sup>b</sup> *P.N.Lebedev Physics Institute, Leninskii prospect 53, 117924, Moscow, Russia*

(February 1, 2008)

We investigate the breakdown of BCS superconductivity in *ultrasmall* metallic grains as a function of particle size (characterized by the mean spacing  $d$  between discrete electronic eigenstates), and the parity ( $P = \text{even/odd}$ ) of the number of electrons on the island. Assuming equally spaced levels, we solve the parity-dependent BCS gap equation for the order parameter  $\Delta_P(d, T)$ . Both the  $T = 0$  critical level spacing  $d_{c,P}$  and the critical temperature  $T_{c,P}(d)$  at which  $\Delta_P = 0$  are parity dependent, and both are so much smaller in the odd than the even case that these differences should be measurable in current experiments.

PACS numbers: 74.20.Fg, 74.80.Fp, 74.80.Bj

The study of the properties of ultrasmall metallic particles has witnessed a dramatic development during the last year: using an ingenious new fabrication technique, Black, Ralph and Tinkham (BRT) [1] have constructed a single-electron transistor (SET) whose island, a single nm-scale Al grain, is more than four orders of magnitude smaller in volume (estimated radii between  $r \sim 2.5$  and 13 nm) than that of conventional SETs. Thus a new energy scale, the average level spacing  $d = 1/N(\varepsilon_F)$  between discrete electronic levels, enters the problem: Both the free-electron estimate of  $d \simeq 2\pi^2\hbar^2/(mk_F V)$  and direct observation (discrete steps in the  $I$ - $V$  curve) give values of  $d$  ranging from 0.02 to 0.3 meV, the latter being much larger than the smallest accessible temperatures ( $\simeq 30$  mK) and on the order of the bulk superconducting gap ( $\Delta_b = 0.18$  meV for Al).

The eigenenergies of the larger grains ( $r > 5$  nm) studied by BRT revealed the existence of an excitation gap  $\Omega > d$  which is driven continuously to zero by an applied magnetic field, and striking gap-dependent parity effects, i.e. differences between islands with an even or odd [ $P = e/o$ ] number of electrons. BRT very convincingly interpreted these phenomena as evidence for superconductivity. On the other hand, in smaller particles ( $r < 5$  nm) it was not possible to detect an  $H$ -dependent gap or other evidence for superconductivity.

These experiments invite reconsideration of an old but fundamental question: *what is the lower size limit for the existence of superconductivity in small grains?* Anderson addressed this question already in 1959 [2] and argued that “superconductivity would no longer be possible” if the level spacing  $d$  becomes larger than the bulk gap  $\Delta_b$ , for reasons explained below. This answer – although in general correct – is not yet quite complete, since it does not address *parity effects*. Even in “large” superconducting islands (with  $d \ll \Delta_b$ ) experiments [3] have demonstrated the dramatic impact of parity on  $I$ - $V$  characteristics; moreover theory [4,5] predicts an even-odd difference for the *superconducting order parameter itself* of  $\Delta_e - \Delta_o = d/2$  at  $T = 0$ . Though the latter dif-

ference is immeasurably small in “large” islands, it should certainly become significant in ultrasmall grains. Moreover, since the crossover temperature at which parity effects become observable [3], namely  $T_{cr} = \Delta_b / \ln N_{eff}$  (where in the  $d \ll \Delta_b$  limit  $N_{eff} = \sqrt{8\pi T \Delta_b / d}$ ), becomes of order  $\Delta_b$  when  $d \simeq \Delta_b$ , parity effects should survive to temperatures as high as  $T_c$  itself. Hence  $T_{c,P}(d)$  as function of  $d$  should be parity-dependent too.

In this Letter we address these issues by studying parity effects in the order parameter  $\Delta_P(d, T)$  for general  $d$ . In particular, we calculate  $\Delta_P(d, 0)$  and  $T_{c,P}(d)$  by solving the BCS gap equation (derived using parity-projected mean-field theory [4,5]) at  $T = 0$  and  $\Delta_P = 0$ , respectively, for the case of equally-spaced single-particle levels. We find  $T_{c,o}(d)/T_{c,e}(d) < 1$  and a remarkably small ratio of critical level spacings  $d_{c,o}/d_{c,e} = 1/4$  at  $T = 0$ . Our results are completely compatible with BRT’s observations. Moreover, the predicted parity differences should be directly observable in their latest experiments which have variable gate voltage, allowing them to change the number parity of a given grain at will.

*The model:* In BRT’s experiments, the charging energy  $E_C = e^2/2C_{total}$  of an ultrasmall grain is by far the largest energy scale in the problem (with  $E_C \simeq 4$  meV  $\gg \Delta_b$ ), so that fluctuations in particle number are strongly suppressed. Therefore, in this Letter we consider a completely isolated grain, which should be described using a canonical ensemble with a prescribed number of electrons  $n = 2m + p$ , where  $p = (0, 1)$  for  $P = (e, o)$  (the labels  $p$ ,  $P$  and also  $n$  will be used interchangeably as parity labels below). We adopt a model Hamiltonian having the standard reduced BCS form:

$$\hat{H} = \sum_{j\sigma} \varepsilon_j^0 c_{j\sigma}^\dagger c_{j\sigma} - \lambda d \sum_{ij} ' c_{i+}^\dagger c_{i-}^\dagger c_{j-} c_{j+} . \quad (1)$$

Here  $c_{j\sigma}^\dagger$  creates an electron in the particle-in-a-box-like, independent-electron state  $|j\sigma\rangle$ , where the states  $|j+\rangle$  and  $|j-\rangle$  are degenerate, time-reversed partners whose energies  $\{\varepsilon_j^0\}$  are considered as a given set of phenomenological parameters. The integer  $j$  is a discrete quantum

number. For a given  $n = 2m + p$ , we take  $j = 0$  to describe the first energy level whose occupation in the  $T=0$  Fermi sea is not 2 but  $p$ , so that  $j = -m, \dots, \infty$ . Finally, the dimensionless coupling constant  $\lambda^{-1} = \ln \frac{2\omega_c}{\Delta}$  is regarded as a phenomenological parameter determined by the value  $\hat{\Delta} \equiv \Delta(0,0)$  of the effective gap (measured at  $d \ll \hat{\Delta}$ ) and some cut-off frequency  $\omega_c$ .

*Pair-mixing:* At this point it seems appropriate to briefly address the question of what is meant by the “existence of superconductivity” in ultrasmall grains. It deserves special attention, firstly because the BCS order parameter  $\Delta$ , if defined as usual by  $\lambda d \sum_j \langle c_{j-} c_{j+} \rangle$ , seems to be zero in a canonical ensemble, and secondly because most of the standard criteria, e.g. a gap followed by a continuous excitation spectrum, zero resistivity and the Meissner effect, are not applicable here.

Now, the microscopic reason for all of these (large-sample) phenomena is of course the *existence of a pair-correlated ground state*. The essence of its correlations is what we shall call *pair-mixing* across  $\varepsilon_F$ , namely the partial population (with amplitude  $v_j > 0$ ) of some time-reversed pairs of states ( $|j+\rangle, |j-\rangle$ ) above  $\varepsilon_F$  ( $j > 0$ ) by partially depopulating (with amplitude  $u_j > 0$ ) some pairs of states below  $\varepsilon_F$  ( $j < 0$ ). This creates phase space for pair scattering (which is Pauli-blocked in the normal ground state) and hence allows the BCS interaction to lower the ground state energy.

Although BCS showed that a brilliantly simple way of calculating the  $u_j$  and  $v_j$  is to use grand-canonical methods, pair-mixing of course can and does also occur in a fixed- $n$  system. Indeed, this pair-mixing can readily be characterized by a “generalized” order parameter that is equal to the conventional  $\lambda d \sum_j \langle c_{j-} c_{j+} \rangle$  in BCS’s grand-canonical mean-field treatment, but (in contrast to the latter expression) is meaningful in a fixed- $n$  system too, namely  $\lambda d \sum_j u_j v_j$ . An experimental signature of this pair-mixing is the energy cost needed to add or remove single electrons that perturb these correlations (i.e. that “break pairs”). Since BRT quite unambiguously measured such energy costs in their larger grains, it seems reasonable to regard these as “superconducting”, in the sense of having a *pair-correlated ground state that measurably exhibits pair-mixing*.

The notion of pair-mixing also provides a simple way to understand why superconductivity ceases to exist in sufficiently small samples. If the level spacing becomes sufficiently large ( $d \simeq \hat{\Delta}$ ), pair-mixing costs a prohibitive amount of kinetic energy and hence ceases to occur. The task at hand is to describe this breakdown (semi-)quantitatively, while keeping track of parity effects.

*Canonical and Parity Projection:* Since in practice it is so much harder to calculate  $u_j, v_j$  canonically than grand-canonically, and since the latter approach has been remarkably successful even in small systems such as nuclei with as little as  $n \sim 100$  nucleons [6], purely canonical descriptions (pioneered by Schafroth [7]) are seldom used.

An alternative approach [4,5] is to employ an auxiliary parity-projected grand-canonical partition function,

$$Z_P^G(\mu) \equiv \text{Tr}^G \frac{1}{2} [1 \pm (-)^{\hat{N}}] e^{-\beta(\hat{H} - \mu \hat{N})} \equiv e^{-\beta \Omega_P^G(\mu)}, \quad (2)$$

( $\text{Tr}^G$  denotes a grand-canonical trace), from which the desired fixed- $n$  partition function  $Z_n$  can in principle be exactly projected by integration:

$$Z_n = \int_{-\pi}^{\pi} \frac{du}{2\pi} e^{-iun} Z_P^G(iu/\beta). \quad (3)$$

Since in practice, though, it is hard to perform the integration exactly, we approximate the integral by its saddle point value,  $Z_n \simeq e^{-\beta \mu_n n} Z_P^G(\mu_n)$ , where  $\mu_n$  is fixed by

$$n = -\partial_{\mu} \Omega_P^G(\mu) \Big|_{\mu=\mu_n} \quad [ = \langle \hat{N} \rangle_P ] \quad (4)$$

(Here  $\langle \rangle_P$  is taken in the parity-projected grand-canonical ensemble of  $Z_P^G$ .) This equation, the bracketed part of which is the parity-projected version of a standard grand-canonical identity, illustrates the elementary fact that the saddle point approximation produces nothing but the grand-canonical description we had set out to improve upon. Nevertheless, the merits of the above approach are that (i) corrections can be calculated systematically by including Gaussian contributions [governed by  $(\langle N^2 \rangle - \langle N \rangle^2)^{-1/2}$ ] to the integral (3) (at  $T=0$  they are  $\sim (d/\Delta)^{1/2}$  [4]); (ii) it illustrates that the parity projection of Eq. (2), which is essential for extracting  $e/o$  differences, can be done exactly even when the fixed- $n$  projection cannot; (iii) it clarifies that in a canonical ensemble  $\mu_n$  is simply the saddle-point value of an integration parameter, which, however, has to be determined with special care in ultrasmall grains, for which  $d$  is large.

*Mean-Field Approximation:* We evaluate  $Z_P^G$  using a “naive mean-field approach” (our method is equivalent to that used in [5]): Make the replacement

$$c_j - c_{j+} \rightarrow \{c_j - c_{j+} - \langle c_j - c_{j+} \rangle_P\} + \langle c_j - c_{j+} \rangle_P \quad (5)$$

in  $\hat{H} - \mu_n \hat{N}$ , neglect terms quadratic in the fluctuations represented by  $\{ \}$  and diagonalize, using  $\gamma_{nj\sigma} = u_{nj} c_{nj\sigma} - \sigma v_{nj} c_{nj-\sigma}^\dagger$ . One obtains the usual results  $\hat{H} - \mu_n \hat{N} \simeq C_n + \sum_{j\sigma} E_{nj\sigma} \gamma_{nj\sigma}^\dagger \gamma_{nj\sigma}$ , where  $E_{nj\sigma} = [\varepsilon_{nj}^2 + \Delta_P^2]^{1/2}$ ,  $\varepsilon_{nj} \equiv \varepsilon_j^0 - \mu_n$ , and  $v_{nj}^2 = \frac{1}{2}(1 - \varepsilon_{nj}/E_{nj})$ . Moreover, since the parity of electron number and quasiparticle number are always the same, Eq. (2) can be rewritten [4] using quasiparticle-parity projection,  $Z_P^G(\mu_n) = \frac{1}{2}(Z_+^G \pm Z_-^G)$ , where

$$Z_{\pm}^G(\mu_n) = e^{-\beta C_n} \prod_{j\sigma} (1 \pm e^{-\beta E_{nj\sigma}}). \quad (6)$$

The usual mean-field self-consistency condition  $\Delta_P = \lambda d \sum_j \langle c_{j-} c_{j+} \rangle_P$  takes the form

$$\frac{1}{\lambda} = d \sum_{|j| < \omega_c/d} \frac{1}{2E_{nj}} \left( 1 - \sum_{\sigma} f_{nj\sigma} \right), \quad (7)$$

where  $f_{nj\sigma} = \langle \gamma_{nj\sigma}^\dagger \gamma_{nj\sigma} \rangle_P$  is given by [4,5]

$$f_{nj\sigma} = -\frac{\partial}{\partial E_{nj\sigma}} \ln Z_P^G(\mu_n) = f_{nj\sigma}^+ + \frac{f_{nj\sigma}^- - f_{nj\sigma}^+}{1 + (-)^p R}. \quad (8)$$

Here we defined  $f_{nj\sigma}^\pm \equiv \pm(e^{\beta E_{nj\sigma}} \pm 1)^{-1}$  and  $R \equiv \frac{Z_P^G}{Z_{-P}^G}$ . The above description thus involves the usual BCS quasiparticles, but *their number parity is restricted to be p*.

Corrections to the naive mean-field expressions for  $E_{nj\sigma}$  and  $\Delta_P$  [as measured, e.g., by fluctuations in  $\Delta_P$ , or by  $(\lambda d \partial_\Delta^2 \Omega_P^G)^{-1/2}$ ] can be shown to be of order  $\lambda d / \Delta$ . Janko *et al.* [4] calculated the leading one of these corrections (their  $1/N_{eff}$  terms) by using a more careful mean-field approach which incorporates contributions from the  $\{ \}^2$  terms neglected above. However, for  $\lambda d / \Delta$  sufficiently large that these terms matter, other non-mean-field corrections ( $\simeq (\lambda d / \Delta)^{1/2}$ ) matter too. Nevertheless, since our goal is merely to find a criterion for when pair-mixing correlations cease to exist, and one such criterion is to establish when the mean-field gap equation no longer has a solution, we shall neglect all corrections going beyond naive mean-field theory.

*Determination of  $\mu_n$ :* Following [8], let us henceforth consider the case of equal level spacing,  $\varepsilon_j^0 = j d + \varepsilon_0^0$  (which seems reasonable for large  $n$ , due to level repulsion). Using  $\langle \hat{N} \rangle_P = \sum_{j\sigma} (v_{nj}^2 + (u_{nj}^2 - v_{nj}^2) f_{nj\sigma})$  and symmetrizing the  $j$ -summation interval by dropping the negligibly small  $j > m - \delta_{P,e}$  terms, Eq. (4) gives [4]

$$2m + p = \sum_{j=-m}^{m-\delta_{P,e}} \left[ 2\theta(\varepsilon_{nj}) + \left\{ \text{sign}(\varepsilon_{nj}) - \frac{\varepsilon_{nj}}{E_{nj}} \right\} + \frac{\varepsilon_{nj}}{E_{nj}} 2f_{nj} \right].$$

Here we have added and subtracted  $\sum_j \text{sign}(\varepsilon_{nj})$  (defining  $\text{sign}(0) \equiv 0$  and  $\theta(0) \equiv \frac{1}{2}$ ). By inspection, this implies that  $\mu_n = \varepsilon_0^0 - \frac{1}{2} d \delta_{P,e}$ , because then  $\varepsilon_{nj} = d(j + \frac{1}{2} \delta_{P,e})$ , which ensures firstly that  $2\theta(\varepsilon_{n0}) = p$ , and secondly that the summands of the second and third terms are anti-symmetric, so that these terms vanish. (More generally, they vanish also for non-equally-spaced levels as long as the levels are distributed roughly symmetrically about  $\varepsilon_0^0$ , in which case  $\mu_n \simeq \varepsilon_0^0 \delta_{P,o} + \frac{1}{2}(\varepsilon_0^0 - \varepsilon_{-1}^0) \delta_{P,e}$ .) Thus we have proven the seemingly obvious: in the language of the  $T=0$  normal Fermi sea,  $\mu_n$  lies exactly half-way between the last filled and first empty levels if  $P$ =even, and exactly on the singly occupied level if  $P$ =odd.

We are now ready to study the gap equation (7).

*Gap Equation at  $T=0$ :* The quasiparticle occupation function reduces to  $f_{nj\sigma} = \frac{1}{2} \delta_{j0} \delta_{P,o}$  at  $T=0$ , as intuitively expected, because then the even or odd systems have exactly zero or one quasiparticle, the latter in the lowest quasiparticle state, namely  $j=0$ . This  $e/o$  difference has a strong impact on the  $T=0$  gap equation: in

the odd case, the  $j=0$  level, for which  $E_{nj}^{-1}$  is largest, is *absent*, reflecting the fact that the odd quasiparticle in the  $j=0$  state obstructs pair scattering involving this state. To compensate this missing term,  $\Delta_o$  must therefore become significantly smaller than  $\Delta_e$  as soon as  $d$  is large enough that a single term becomes significant relative to the complete sum.

To quantify this statement, it is convenient to rewrite Eq. (7) at  $T=0$  as follows: Writing  $E_{nj}^{-1} = \int d\omega / \pi (E_{nj}^2 + \omega^2)^{-1}$ , transferring the cut-off  $\omega_c$  from  $\sum_j$  to  $\int d\omega$ , and performing the  $j$ -sum (by contour integration) gives

$$\ln \frac{2\omega_c}{\tilde{\Delta}} = \int_0^{\omega_c} \frac{d\omega}{E_{P\omega}} \left[ (\tanh \pi E_{P\omega} / d)^{1-2p} - \frac{d \delta_{P,o}}{\pi E_{P\omega}} \right], \quad (9)$$

where  $E_{P\omega} = (\omega^2 + \Delta_P^2)^{1/2}$ . Since, amusingly, for  $P=e$  Eq. (9) is identical in form (with  $d \rightarrow 2\pi T$ ) to the well-known gap equation for the  $T$ -dependence of the bulk gap (curve A in Fig. 1), we have  $\Delta_e(d, 0) = \Delta_P(0, d/2\pi)$ . Thus, for  $d/\tilde{\Delta} \ll 1$  the even gap has the standard form  $\Delta_e(d, 0) = \tilde{\Delta}(1 - \sqrt{\tilde{\Delta} d} e^{-2\pi \tilde{\Delta}/d})$ ; in contrast, one easily finds from Eq. (9) that the odd gap drops linearly,  $\Delta_o(d, 0) = \tilde{\Delta} - d/2$ , in agreement with [4,5].

The full solutions of Eq. (9) for  $\Delta_P(d, 0)$ , obtained numerically, are shown as curves B and C in Fig. 1. The critical values  $d_{c,P}$  at which  $\Delta_P(d_{c,P}, 0) = 0$  can be found analytically by setting  $\Delta_P = T = 0$  in Eq. (7):

$$\frac{d_{c,e}}{\tilde{\Delta}} = 2e^\gamma \simeq 3.56 \quad \text{and} \quad \frac{d_{c,o}}{\tilde{\Delta}} = \frac{1}{2} e^\gamma \simeq 0.890. \quad (10)$$

*Critical temperature:* Although ultrasmall grains cannot undergo a sharp thermodynamic phase transition (this would require  $n \rightarrow \infty$ ), the quantity  $T_{c,P}(d)$ , defined simply as the solution to the  $\Delta_P \rightarrow 0$  limit of Eq. (7), is another measure of how rapidly pair-mixing correlations break down as function of level spacing. Our numerical results for  $T_{c,P}(d)$  [10], shown as curves D and E of Fig. 1 for  $P=e/o$ , have the expected limits at  $d=0$  and  $d_{c,P}$ , but behave unexpectedly in between:

*Even:* In the even case,  $T_{c,e}(d)$  is non-monotonic, increasing slowly from its initial value  $T_{c,e}(0) = \tilde{\Delta} e^\gamma / \pi = 0.567 \tilde{\Delta}$  to a maximum given by  $T_{c,e}(2.60 \tilde{\Delta}) = 0.736 \tilde{\Delta} > T_{c,e}(0)$ . It then drops to zero very rapidly as  $T_{c,e}(d) \simeq d / \log[4d_{c,e}/(d_{c,e} - d)]$ , which follows from setting  $\Delta_e = 0$  in  $\Delta_e(d, T) \simeq d [2(1 - d/d_{c,e} - 4e^{-d/T}) / (7\zeta(3))]^{1/2}$ , an analytical result that holds for the regime  $T, \Delta_e(T) \ll d$ . The intuitive reason for the initial increase in  $T_{c,e}(d)$  is that the difference between the actual and the usual quasiparticle occupation functions is  $f_{nj\sigma} - f_{nj\sigma}^+ < 0$  for an even grain (becoming significant when  $d \simeq \tilde{\Delta}$ ), reflecting the fact that exciting quasiparticles two at a time is more difficult than one at a time. Therefore the quasiparticle-induced break-down of superconductivity with increasing  $T$  will set in at slightly higher  $T$  if  $d \simeq \tilde{\Delta}$ .

*Odd:* In the odd case,  $T_{c,o}(d)$  “overshoots” a bit near  $d = d_{c,o}$ , or alternatively, the critical level spacing  $d_{c,o}(T)$

is non-monotonic as a function of increasing  $T$ , reaching a maximum value given by  $d_{c,o}(0.387\tilde{\Delta}) = 1.05\tilde{\Delta}$  before beginning to decrease. The intuitive reason for this is that for  $0 < \Delta_o \ll T, d$  the odd  $j = 0$  function  $f_{n0\sigma}(T)$  becomes somewhat smaller than its  $T = 0$  value of  $\frac{1}{2}$ , because with increasing  $T$  some of the probability for finding a quasiparticle in state  $j$  “leaks” from  $j = 0$  to higher states with  $j \neq 0$ , for which  $E_{nj}^{-1} < E_{no}^{-1}$  in Eq. (7). Thus, the dramatic blocking-of-pair-scattering effect of the odd quasiparticle becomes slightly less dramatic as  $T$  is increased, so that  $d_{c,o}$  increases slightly.

*Discussion:* An important general feature of our results is that level discreteness *always reduces*  $\Delta_P(d, 0)$  to be  $< \tilde{\Delta}$  (thus contradicting Ref. [9], which was convincingly criticised in Ref. [8]). However, BRT’s experiment found an effective gap  $\tilde{\Delta}$  that is larger by a factor of 1.5 to 2 than its bulk value  $\Delta_b$ . Following the argumentation of [8] for thin films, we can attribute this to presumed changes in the phonon spectrum in small samples, which can be modeled by using a constant value of  $\lambda$  larger (by a few percent) than the usual bulk value  $\lambda_b$ .

The rather rapid drop of  $\Delta_P(d)$ , once it happens, could be the reason why BRT see a well-developed gap  $\tilde{\Delta}$  even for  $d \simeq \tilde{\Delta}$ , but don’t see any for their smallest grains. The most important conclusion of this paper, though, is summarized by Fig. 1 and Eq. (10): there is a large regime in which  $\Delta_o = 0$  while  $\Delta_e$  is still  $\simeq \tilde{\Delta}$ , in other words, *pair-mixing correlations vanish significantly sooner for odd than even grains as their size is reduced*. Moreover, the surprising largeness of the ratio  $d_{c,e}/d_{c,o} = 4$  opens the exciting possibility of studying grains with  $d_{c,o} < d < d_{c,e}$ , which should have  $\Delta_o = 0$  while  $\Delta_e$  is still  $\simeq \tilde{\Delta}$ . Since this leaves tell-tale traces in the  $I$ - $V$ - $V_g$  characteristics [10], BRT should be able to test this prediction directly, since they can change the electron parity of a given grain in a controlled way by tuning the gate voltage of their SET, and hence study the *same* grain in both its even and odd states.

Of course, a nagging question remains: How robust are our mean-field-based results? Will not fluctuations in  $\Delta$ , governed by  $d/\tilde{\Delta}$  and hence large in ultrasmall grains, wash out the predicted parity differences in  $\Delta_{e/o}$ ? For instance, it is doubtful that the unexpected non-monotonic subtleties of  $T_{c,P}(d)$ , though intuitively plausible, have physical significance, since they fall in the  $\Delta_P \simeq 0$  regime where fluctuations are extremely large.

However, while a detailed analysis of the fluctuations is beyond the scope of this Letter, we believe that, at least in the (experimentally accessible) regime of  $T/d \simeq 0$ , our main result is indeed robust: Firstly, it is known that at  $T = 0$ , the leading  $d/\tilde{\Delta}$  fluctuation corrections to the free energy difference  $\Omega_e^G - \Omega_o^G$  are parity-independent [4,5]. Secondly, since as  $d$  approaches the point where  $\Delta_o$  vanishes, we have  $d/\Delta_e \lesssim 1 \ll d/\Delta_o$ , fluctuations become important much later in the even than the odd

case. Thirdly, even for systems much smaller than ultrasmall grains (that have  $n \sim 10^4$ ), namely shell model nuclei (with  $n \sim 100$ ), the  $T = 0$  BCS-description of pairing interactions has been remarkably successful [6], despite the presence of large fluctuations.

The perhaps most compelling support for the reality of the predicted effect comes from the following back-of-the-envelope argument: the ground state energy difference between a BCS superconductor with parity  $P$  and the normal Fermi sea is  $-\tilde{\Delta}_P^2/(2d) + \tilde{\Delta}_o\delta_{P,o}$ . While for  $P = e$  it is always negative, for  $P = o$  it vanishes when  $d > \frac{1}{2}\tilde{\Delta}$ , illustrating that the odd electron indeed dramatically disrupts pair-mixing correlations when  $d \simeq \tilde{\Delta}$ .

In conclusion, we have investigated the influence of parity on the superconducting mean-field order parameter in ultrasmall grains. We have found that as a function of decreasing grain size, superconductivity breaks down in an odd grain significantly earlier than in an even grain, which should be observable in present experiments.

It is a pleasure to thank BRT for showing us their preliminary results, and to acknowledge discussions with

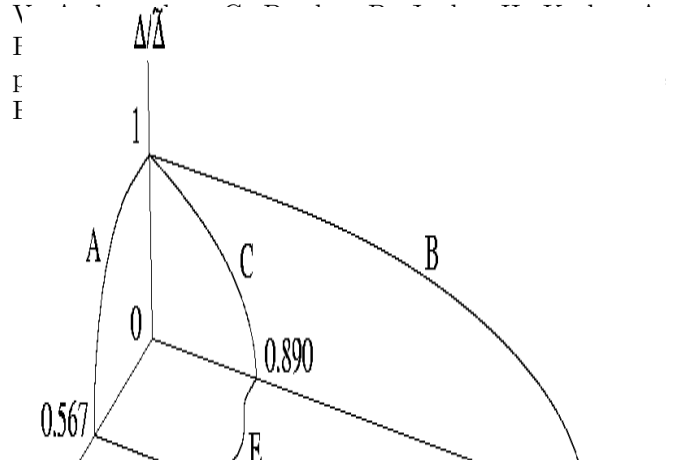


FIG. 1.  $\Delta(d, T)/\Delta$  as a function of  $d/\Delta$  and  $T/\Delta$  for  $P = e$  (curves B, D) and  $P = o$  (curves C, E). Here  $\tilde{\Delta} = \Delta(0, 0)$ .

- [1] C.T. Black, D.C. Ralph and M. Tinkham, Phys. Rev. Lett. **76**, 688 (1996); *ibid.* **74**, 3241 (1995); Physica B **218**, 258 (1996).
- [2] P.W. Anderson, J. Phys. Chem. Solids **11**, 28 (1959).
- [3] M.T. Tuominen, J.M. Hergenrother, T.S. Tighe and M. Tinkham, Phys. Rev. Lett. **69**, 1997 (1992); P. Lafarge *et al.*, Phys. Rev. Lett. **70**, 994 (1993).
- [4] B. Janko, A. Smith, and V. Ambegaokar, Phys. Rev. B **50**, 1152 (1994).
- [5] D.S. Golubev and A.D. Zaikin, Phys. Lett. A **195**, 380 (1994).
- [6] F. Iachello, Nucl. Phys. A **570**, 145c (1994).
- [7] J.M. Blatt, *Theory of Superconductivity*, Academic Press (1964).
- [8] M. Strongin *et al.*, Phys. Rev. B, **1**, 1078 (1970).
- [9] R.H. Parmenter, Phys. Rev. **166**, 392 (1968).
- [10] Wolfgang Tichy and Jan von Delft, to be published.